



A Review of Powder Bed Fusion for Additively Manufactured Ti-6wt.%Al-4wt.%V

McFadden, S., Quinn, JP., & Harkin, R. (2018). *A Review of Powder Bed Fusion for Additively Manufactured Ti-6wt.%Al-4wt.%V*. Paper presented at The 35th International Manufacturing Conference, Dublin, Ireland.

[Link to publication record in Ulster University Research Portal](#)

Publication Status:

Published (in print/issue): 20/07/2018

Document Version

Author Accepted version

General rights

The copyright and moral rights to the output are retained by the output author(s), unless otherwise stated by the document licence.

Unless otherwise stated, users are permitted to download a copy of the output for personal study or non-commercial research and are permitted to freely distribute the URL of the output. They are not permitted to alter, reproduce, distribute or make any commercial use of the output without obtaining the permission of the author(s).

If the document is licenced under Creative Commons, the rights of users of the documents can be found at <https://creativecommons.org/share-your-work/ccllicenses/>.

Take down policy

The Research Portal is Ulster University's institutional repository that provides access to Ulster's research outputs. Every effort has been made to ensure that content in the Research Portal does not infringe any person's rights, or applicable UK laws. If you discover content in the Research Portal that you believe breaches copyright or violates any law, please contact pure-support@ulster.ac.uk

A Review of Powder Bed Fusion for Additively Manufactured Ti-6wt.%Al-4wt.%V

Ryan Harkin¹, Dr Justin Quinn¹, Dr Shaun McFadden¹

School of Computing, Engineering, and Intelligent Systems; Ulster University; Magee Campus; BT48 7JL;UK

Harkin-r7@ulster.ac.uk

Abstract

Selective Laser Melting (SLM) a form Powder Bed Fusion (PBF), is a type of Additive Manufacturing (AM) process which has the ability to manufacture complex geometric parts that cannot be produced by traditional means. Ti₆Al₄V is an $\alpha + \beta$ titanium alloy and is commonly used within the medical and aerospace industries. It is one of the few technical metal alloys that can be processed by PBF. This contribution will review the issues related to microstructure formation, residual stress, and porosity formation that can arise within Ti₆Al₄V parts produced by the PBF process. In particular, the influence of the manufacturing process parameters and the presence of defects on the mechanical properties will be reviewed. High thermal gradients and rapid solidification of the molten powder can lead to the development of a martensitic microstructure and other specific defects within the as-built part. Defects have a negative impact upon mechanical properties. Porosity, balling, lack of fusion and delamination are common examples of process-specific defects. The requirement for secondary processing of the additively manufactured components to improve mechanical properties will be reviewed with a particular focus on the requirement for the Hot Isostatic Pressing (HIP) processing.

Keywords: Additive Manufacturing, Selective Laser Melting, Ti₆Al₄V, Defects, Hot Isostatic Pressing

1. INTRODUCTION

SLM a form of PBF, is one of seven types of AM processes identified according to (ISO/ASTM 52900:2015, Additive Manufacturing). Defining AM by a process of joining materials to make parts from 3D model data, usually layer on layer. Hence allowing parts with a high complex structure to be manufactured, otherwise unachievable by traditional methods. According to BS ISO/ASTM 52910-17, the PBF process uses an energy source to melt the powder particles to form part cross-sections. The deposited powder upon the preheated platform, forms a melt pool upon exposure with the high temperature laser. The rate at which the melt pool solidifies, determines the formation of the microstructure. The present phases, grain morphology and the distribution of the microstructure defines the part properties. Ti₆Al₄V is an $\alpha + \beta$ metal alloy where the 6wt% aluminium stabilises the α phase and the 4wt% vanadium stabilises the β phase. Approximately 60% of employed titanium alloys

produced are Ti₆Al₄V. The Ti₆Al₄V alloy is commonly used in aerospace and medical industries due to its high specific strength, good fatigue resistance and biocompatibility properties.

2. DEFECTS

Despite the process specific benefits, numerous as-built characteristics require resolving to acquire an acceptable part for application. Porosity, martensitic microstructure and residual stress are examples of commonly found defects which arise via the SLM process, negatively impacting the part properties. Rapid solidification of the molten Ti₆Al₄V powder, promotes formation of acicular martensite. Associating high tensile strength and poor ductility part properties. Leuders et al. (Leuders *et al.*, 2013) showed that pores have a significant impact on fatigue behaviour, initiating crack growth. Pore generation is a result of powder contamination, evaporation or local voids after deposition of the layers. High thermal gradients and rapid solidification within the SLM process, encourages the development of residual stress. Having a strong impact upon crack initiation and growth, promoting failure. Reduction or elimination of defects from SLM parts can be achieved via process optimisation or post-processing. For this to transpire, the relationship between the processing parameters, microstructure and mechanical properties is critical in developing an application-specific part.

2.1 MICROSTRUCTURE

Cyclic heat treatments exist throughout the build of SLM components. Consequently, the microstructure is always stressed, orientated and segregated from rapid solidification, directional cooling and complex thermal history. The cooling rate of the melt pool is dictated by the surrounding ambient temperature or the build platform temperature, within the SLM process. Shunmugavel and Polishetty (Shunmugavel and Polishetty, 2015) compared the microstructure and mechanical properties of wrought and SLM Ti₆Al₄V cylindrical rods. In the longitudinal direction, the wrought bar consisted of full equiaxed microstructure with inter granular β . The microstructure within the as-built SLM Ti₆Al₄V rods was inhomogeneous and consisted of fine acicular α' grains within the β grain boundaries. Consequently, the ultimate tensile strength and yield strength within the SLM rods was higher in comparison with the wrought rods in the transverse direction, as shown in *figure 1*. The percentage of elongation in the as-built SLM rods ranged from 1-7%, compared with the wrought rods ranging from 19-21%.

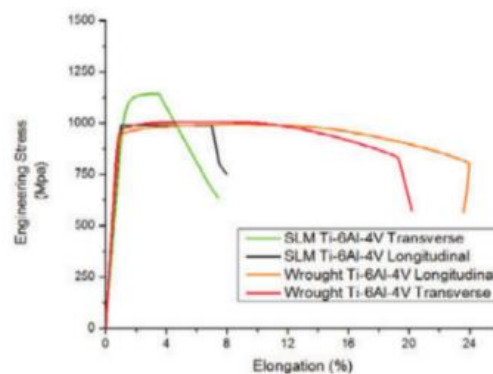


Figure 1- Stress-strain curve for the wrought and SLM Ti-6Al-4V (Shunmugavel and Polishetty, 2015)

2.2 POROSITY

Large thermal stresses and a melt pool instability can generate defects within the as-built part. Porosity, balling effect, lack of fusion and delamination are examples of the typically found defects within SLM Ti₆Al₄V components. Porosity in Ti₆Al₄V has a direct impact upon mechanical properties, in particular fatigue strength promoting crack growth initiation. Porosity within the SLM part can be associated with the energy density (J/mm³), defined as the average energy density per unit volume of material. Zhou et al. (Zhou *et al.*, 2018) showed that the impact the bulk energy density has upon the fine acicular martensite and the lamellar α phase. Bulk energy density below 533J/mm³ was considered to be too low, leading to partial melting of the powder thus forming more equiaxed grains. Kasperovich et al. (Kasperovich *et al.*, 2016) studied the relationship between porosity and the processing parameters of Ti₆Al₄V in SLM. Laser power and laser velocity showed to have the largest impact upon the porosity fractions. A minimum porosity fraction of $0.042 \pm 0.008\%$ was achieved by process optimisation.

The SLM process is becoming an established technique for manufacturing porous metal implants due to the controllability over geometrical and mechanical parameters. The success of a porous biomaterial is relative to the selection of the morphological parameters including the average pore size and porosity. Bulk porosity value above 50% and an average pores size ranging from 50 to 800 μ m is the allowable tolerance for bone growth.

2.3 RESIDUAL STRESS

Large thermal gradients generated with the SLM process leads to a variation in elastic deformation, resulting in high levels of residual stress within the as-built part. Magnitude dependant, this can potentially lead to warping distortion and stress cracking within the SLM component. Ali et al. (Ali *et al.*, 2017) reviewed the effect scan strategy had upon residual stress and mechanical properties within Ti₆Al₄V SLM parts. At a 90° alternating scan strategy, the minimal porosity and residual stress was achieved at 0.1% and 107MPa respectively. Despite, rescanning with a 150% energy density the residual stress reduced by 33%, it had severe permutations upon the mechanical properties causing premature failure. Mugwagwa et al. (Mugwagwa *et al.*, 2018) considered the influence that the laser power, scanning speed and layer thickness in relation to the residual stress distortions. At a laser power of 180W and layer thickness of 30 μ m, the distortion increased from 0.38mm to 1.18mm as the scan speed increased from 400mm/s to 1000mm/s respectively. Vrancken (Vrancken, 2016) stated reduction of residual stress can be achieved by a high laser power, low scan speed, thicker layers, shorter scan vectors and the use of preheating. Preheating of the build platform to 400°C showed a 50% reduction of residual stress. Further research regarding residual stress is required specifically within parts produced by SLM.

3. POST PROCESSING

Despite the capability to optimise the process parameters to limit defects, a heat treatment application generates a part with properties similar or better to the wrought of the same material. Heat treatments

of the Ti₆Al₄V alloy can be categorised into two groups in relation to the heating temperature. Supertransus and Subtransus, whereby the heating temperature is above or below the β transus at 995°C respectively. Zhang et al. (Zhang *et al.*, 2018) reported that all SLM produced Ti₆Al₄V parts when heat treated below the β transus temperature had higher yield strengths and compressive strengths compared with the as-forged counterpart. Heat treatment can transform the microstructure in Ti₆Al₄V parts from acicular martensite to a stable α + β phase, improving mechanical properties.

HIP, a popular heat treatment method for AM parts, utilises high pressures and temperatures to remove the specified defects. Leuders et al. (Leuders *et al.*, 2013) researched the relationship between microstructure, defect and mechanical properties under cyclic loading for SLM processes Ti₆Al₄V parts. The fatigue behaviour was investigated in as-built, heat treated and HIPed Ti₆Al₄V parts. Results showed that the theoretical relative density in five SLM sample parts after HIPing was 100%, as the pore size was reduced below the 22μm detection limit. The average fatigue life for an as-built and heat-treated part ranged from 27,000 to 290,000 cycles to failure. Compared with the HIPed samples were the test was stopped at 2 x 10⁶ cycles, as no sample had undergone failure. Wauthle et al. (Wauthle *et al.*, 2015) explored the effects of build orientation and heat treatments upon the microstructure and mechanical properties of SLM produced Ti₆Al₄V lattice structures. Analysis showed that regardless of the build orientation or unit cell orientation, the three heat treatment conditions examined; as built versus stress relief and HIP, have a clear influence upon mechanical properties. HIP reduced the tensile strength by approximately 15% compared with the as-built part however the strain at fracture increased from 25-70%.

4. Conclusion

Several artefacts relative related to metal additive manufacture or Ti₆Al₄V have been reviewed in this paper. These features include observations of microstructure and unwanted artefacts such as defects (e.g. porosity) and residual stress. An important observation for AM Ti₆Al₄V parts is that to strain to fracture significantly reduced compared to the wrought alloy counterparts. Post processing, particularly HIPing, of the Ti₆Al₄V parts can be utilised to reduce porosity within the as-built part.

REFERENCES

ISO/ASTM 52900:2015, Additive manufacturing, General principles Terminology, Available at: <https://www.iso.org/standard/69669.html> (Accessed: 14 May 2018).

Ali, H. *et al.* (2017) 'In-situ residual stress reduction, martensitic decomposition and mechanical properties enhancement through high temperature powder bed pre-heating of Selective Laser Melted Ti6Al4V', *Materials Science and Engineering: A*. Elsevier, 695, pp. 211–220. doi: 10.1016/J.MSEA.2017.04.033.

ISO/ASTM 52900:2015 - Additive manufacturing -- General principles -- Terminology (no date). Available at: <https://www.iso.org/standard/69669.html> (Accessed: 14 May 2018).

Kasperovich, G. *et al.* (2016) 'Corrigendum to "Correlation between porosity and processing parameters in TiAl6V4 produced by selective laser melting" [Materials and Design 105 (2016) 160–170]', *Materials & Design*, 112, pp. 160–161. doi: 10.1016/j.matdes.2016.09.040.

Leuders, S. *et al.* (2013) 'On the mechanical behaviour of titanium alloy TiAl6V4 manufactured by selective laser melting: Fatigue resistance and crack growth performance', *International Journal of Fatigue*. Elsevier, 48, pp. 300–307. doi: 10.1016/J.IJFATIGUE.2012.11.011.

Mugwagwa, L. *et al.* (2018) 'Influence of process parameters on residual stress related distortions in selective laser melting', *Procedia Manufacturing*. Elsevier, 21, pp. 92–99. doi: 10.1016/J.PROMFG.2018.02.099.

Shunmugavel, M. and Polishetty, A. (2015) 'Microstructure and Mechanical Properties of Wrought and Additive Manufactured Ti-6Al-4 V Cylindrical Bars', *Procedia Technology*. Elsevier, 20, pp. 231–236. doi: 10.1016/J.PROTCY.2015.07.037.

Vrancken, B. (2016) 'Study of Residual Stresses in Selective Laser Melting', *PhD Thesis; KU Leuven Arenberg Doctoral School Faculty of Engineering Science*, (June), pp. 1–253. Available at: https://lirias.kuleuven.be/bitstream/123456789/542751/1/thesis+Bey+Vrancken+v01-06-2016+FINAL_compressed.pdf.

Wauthle, R. *et al.* (2015) 'Effects of build orientation and heat treatment on the microstructure and mechanical properties of selective laser melted Ti6Al4V lattice structures', *Additive Manufacturing*. doi: 10.1016/j.addma.2014.12.008.

Zhang, X.-Y. *et al.* (2018) 'Effect of subtransus heat treatment on the microstructure and mechanical properties of additively manufactured Ti-6Al-4V alloy', *Journal of Alloys and Compounds*. Elsevier, 735, pp. 1562–1575. doi: 10.1016/J.JALLCOM.2017.11.263.

Zhou, B. *et al.* (2018) 'A study of the microstructures and mechanical properties of Ti6Al4V fabricated by SLM under vacuum', *Materials Science and Engineering: A*. Elsevier, 724, pp. 1–10. doi: 10.1016/J.MSEA.2018.03.021.

Acknowledgments

The North West Centre for Advanced Manufacturing (NW CAM) project is supported by the European Union's INTERREG VA Programme, managed by the Special EU Programmes Body (SEUPB). The views and opinions in this document do not necessarily reflect those of the European Commission or the Special EU Programmes Body (SEUPB). If you would like further information about NW CAM please contact the lead partner, Catalyst Inc., for details.