



## Phosphorus-Nitrogen Synergism in Fire Retarding Styrenic Polymers: Some Preliminary Studies

Baby, A., Tretsiakova-McNally, S., Joseph, P., & Zhang, J. (2021). *Phosphorus-Nitrogen Synergism in Fire Retarding Styrenic Polymers: Some Preliminary Studies*. Poster session presented at European Meeting on Fire Retardant Polymeric Materials, Budapest, Hungary.

[Link to publication record in Ulster University Research Portal](#)

### Publication Status:

Published (in print/issue): 01/09/2021

### Document Version

Publisher's PDF, also known as Version of record

### General rights

Copyright for the publications made accessible via Ulster University's Research Portal is retained by the author(s) and / or other copyright owners and it is a condition of accessing these publications that users recognise and abide by the legal requirements associated with these rights.

### Take down policy

The Research Portal is Ulster University's institutional repository that provides access to Ulster's research outputs. Every effort has been made to ensure that content in the Research Portal does not infringe any person's rights, or applicable UK laws. If you discover content in the Research Portal that you believe breaches copyright or violates any law, please contact [pure-support@ulster.ac.uk](mailto:pure-support@ulster.ac.uk).



# Phosphorus-Nitrogen Synergism in Fire Retarding Styrenic Polymers: Some Preliminary Studies

**Aloshy Baby<sup>a</sup>, Svetlana Tretsiakova-McNally<sup>a</sup>, Paul Joseph<sup>b</sup>, and  
Jianping Zhang<sup>a</sup>**

ulster.ac.uk

<sup>a</sup>Belfast School of Architecture and the Built Environment, Ulster University, UK; <sup>b</sup>Institute for Sustainable Industries and Liveable Cities, Victoria University, Australia

## Introduction

The primary strategies to improve the fire retardance of commercially important styrene-based polymers are largely reliant on halogenated fire retardants (FRs). Currently, these compounds are considered to be hazardous to public health and environment. As a result, many halogen-based FRs have been withdrawn, especially, from their use in products that form construction elements in built environments [1]. Thus, it is necessary to develop efficient fire-retardant systems for mitigating their hazardous impact in fire scenarios. Among the proposed FR solutions, the compounds containing P atoms can be very powerful in inhibiting the ignition, and often suppress the combustion of polymeric materials effectively [2].

Here, we report preliminary results on the chemical incorporation of various P- and/or N- containing unsaturated compounds into polystyrene (PS) via co- and *ter*- polymerisations and characterisations of the modified materials with regards to their thermal degradation and combustion attributes. The primary aim of this study to find the effective combination of P- and N- containing compounds that can trigger P-N synergism, thus enhancing fire retardance of PS. The compounds such as diethyl(acryloyloxymethyl)phosphonate (DEAMP), diethyl-*p*-vinylbenzyl phosphonate (DEpVBP), acrylic acid-2-(diethoxyphosphorylamino)ethyl ester (ADEPMAE), maleimide (MI), acrylamide (AM) and N,N-dimethyl acrylamide (DMA) had been used for the modification of PS. The fire performance of unmodified PS and modified PS was determined using a range of standard techniques. They included bomb calorimetry, thermo-gravimetric analysis (TGA), differential scanning calorimetry (DSC), Fourier Transform Infrared (FT-IR) spectroscopy, Nuclear Magnetic Spectroscopy (NMR).

## Materials

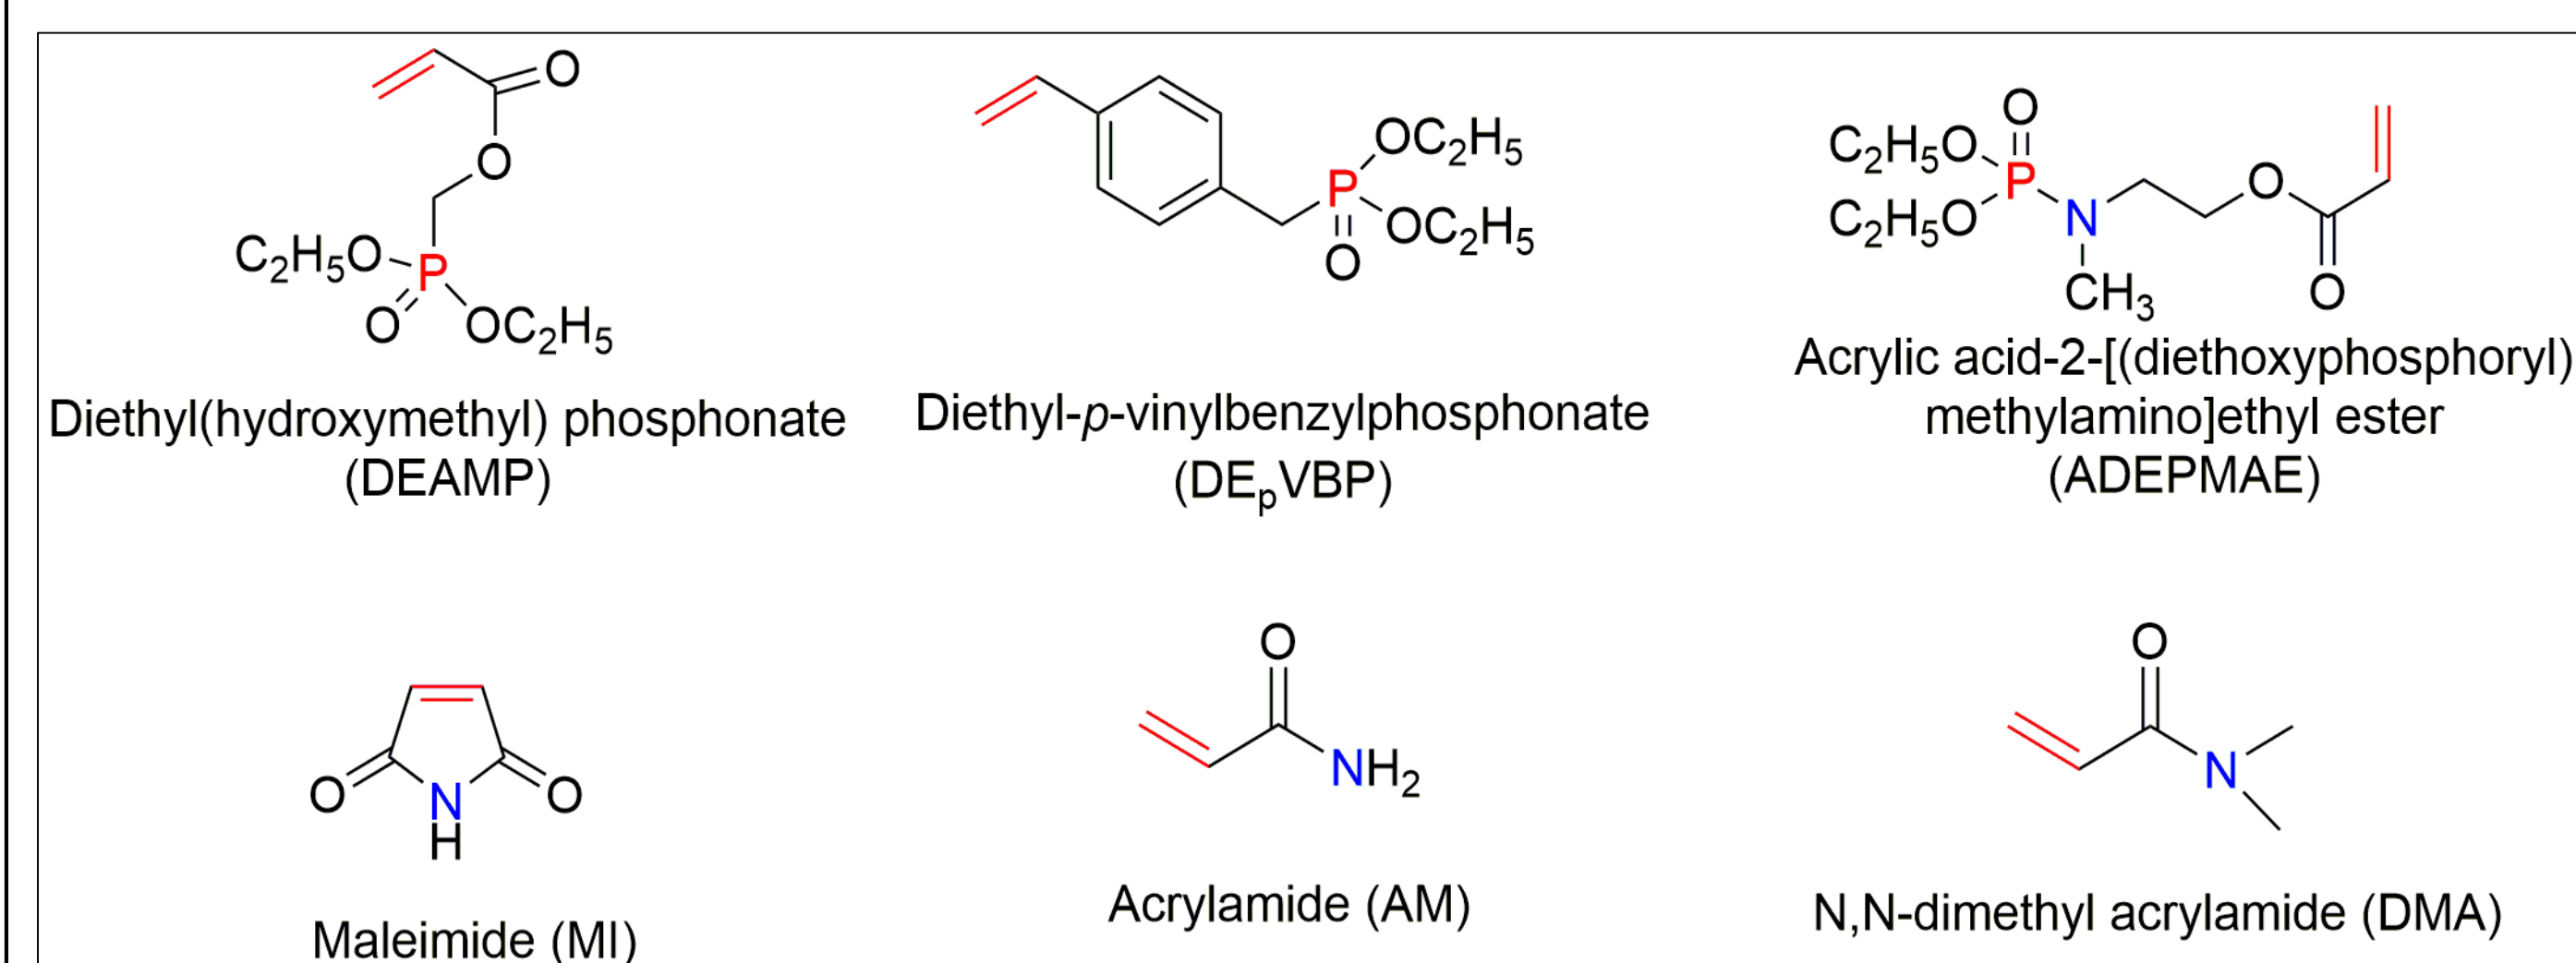


Figure 1: Chemical structures of P-, P/N- and N-containing compounds

## Procedure

- Co- and *ter*-polymers of styrene (St) were primarily prepared through free-radical polymerisation reactions in toluene/DMF using 2,2'-azobisisobutyronitrile (AIBN) as the initiator, at 60 °C for about 6-16 hours, under an atmosphere of argon.
- The polymeric products, were recovered by precipitation into an excess of methanol, followed by drying to constant weight in a vacuum oven kept at ca. 50°C.

## Methods

- Bomb calorimetry: Parr 6200 oxygen bomb calorimeter; gross calorific value measurements as per BS EN ISO 18125:2017
- TGA: Perkin Elmer Pyris 1 TGA instrument, ca. 8-9 mg samples, 30-800 °C temperature range, nitrogen and air atmospheres, at 10 °C/min heating rate.
- DSC: Mettler Toledo DSC 1 system, ca. 8-9 mg samples, 25 -600 °C temperature range, nitrogen atmosphere, at 50ml/min flow and 10 °C/min heating rate.
- Fourier-Transform Infrared (FT-IR) spectra recorded in Attenuated Total Reflectance (ATR) mode on a Thermo Nicolet, Nexus spectrometer

Contact Details: [baby-a1@ulster.ac.uk](mailto:baby-a1@ulster.ac.uk)  
Belfast School of Architecture and the Built Environment, Ulster University,  
Jordanstown, Co. Antrim,  
BT37 0QB, Northern Ireland, UK

## Results

The level of incorporation of monomers (P- and N-) kept as low as possible. The mole fraction of St/monomer in the feed was 0.90/0.10 mol/mol for co-polymers and 0.80/0.10/0.10 for *ter*-polymers. From the flammability and combustion studies of co-polymers, it is evident that all co-polymers of styrene increase the fire efficiency of PS (Table 1). However, it is more evident that styrenic co-polymers with DEAMP, DEpVBP, and MI were more efficient in enhancing fire retardancy of PS. It is clear from the decrease in the values of  $\Delta H_{pyro}$  and  $\Delta H_{comb}$  and increase in the char residue (TGA) of co-polymers such as St-DEAMP, St-DEpVBP and St-MI (Table 1 and figure 2). Therefore, from the list of FRs used for co-polymerisation of styrene, the most effective FRs groups such as DEAMP, DEpVBP and MI were used for preparing *ter*-polymers. The results proved that there is significant drop in  $\Delta H_{pyro}$  and  $\Delta H_{comb}$  of *ter*-polymers compared to that of co-polymers. For instance,  $\Delta H_{comb}$  had reduced by 22.8% and 19.5% for the *ter*-polymers, St-DEAMP-MI and St-DEpVBP-MI respectively.

Table 1: Heat of pyrolysis, heat of combustion and char residue of polymers measured in TGA in nitrogen and air atmosphere

Sample	$\Delta H_{pyro}$ (J/g)	$\Delta H_{comb}$ (J/g)	Residue in N <sub>2</sub> at 500°C (wt %)	Residue in N <sub>2</sub> at 800°C (wt %)	Residue in air at 500°C (wt %)	Residue in air at 800°C (wt %)
PS	717.0	40412	0.6	0.5	0.6	0.1
St-DEAMP	392.9	35453	7.8	6.2	22.3	2.2
St-DEpVBP	673.8	39268	5.4	4.0	17.8	1.9
St-ADEPMAE	701.0	38026	2.7	2.0	8.7	1.4
St-MI	659.6	34059	2.1	1.3	5.5	0.4
St-AM	663.0	39051	0.2	0.2	2.6	0.6
St-DMA	702.7	39963	0.4	0.2	2.6	0.4
St-DEAMP-MI	190.5	31267	25.2	22.2	44.6	3.1
St-DEpVBP-MI	162.3	32520	25.1	21.6	36.1	1.2

$\Delta H_{pyro}$  – heat of pyrolysis,  $\Delta H_{comb}$  – heat of combustion

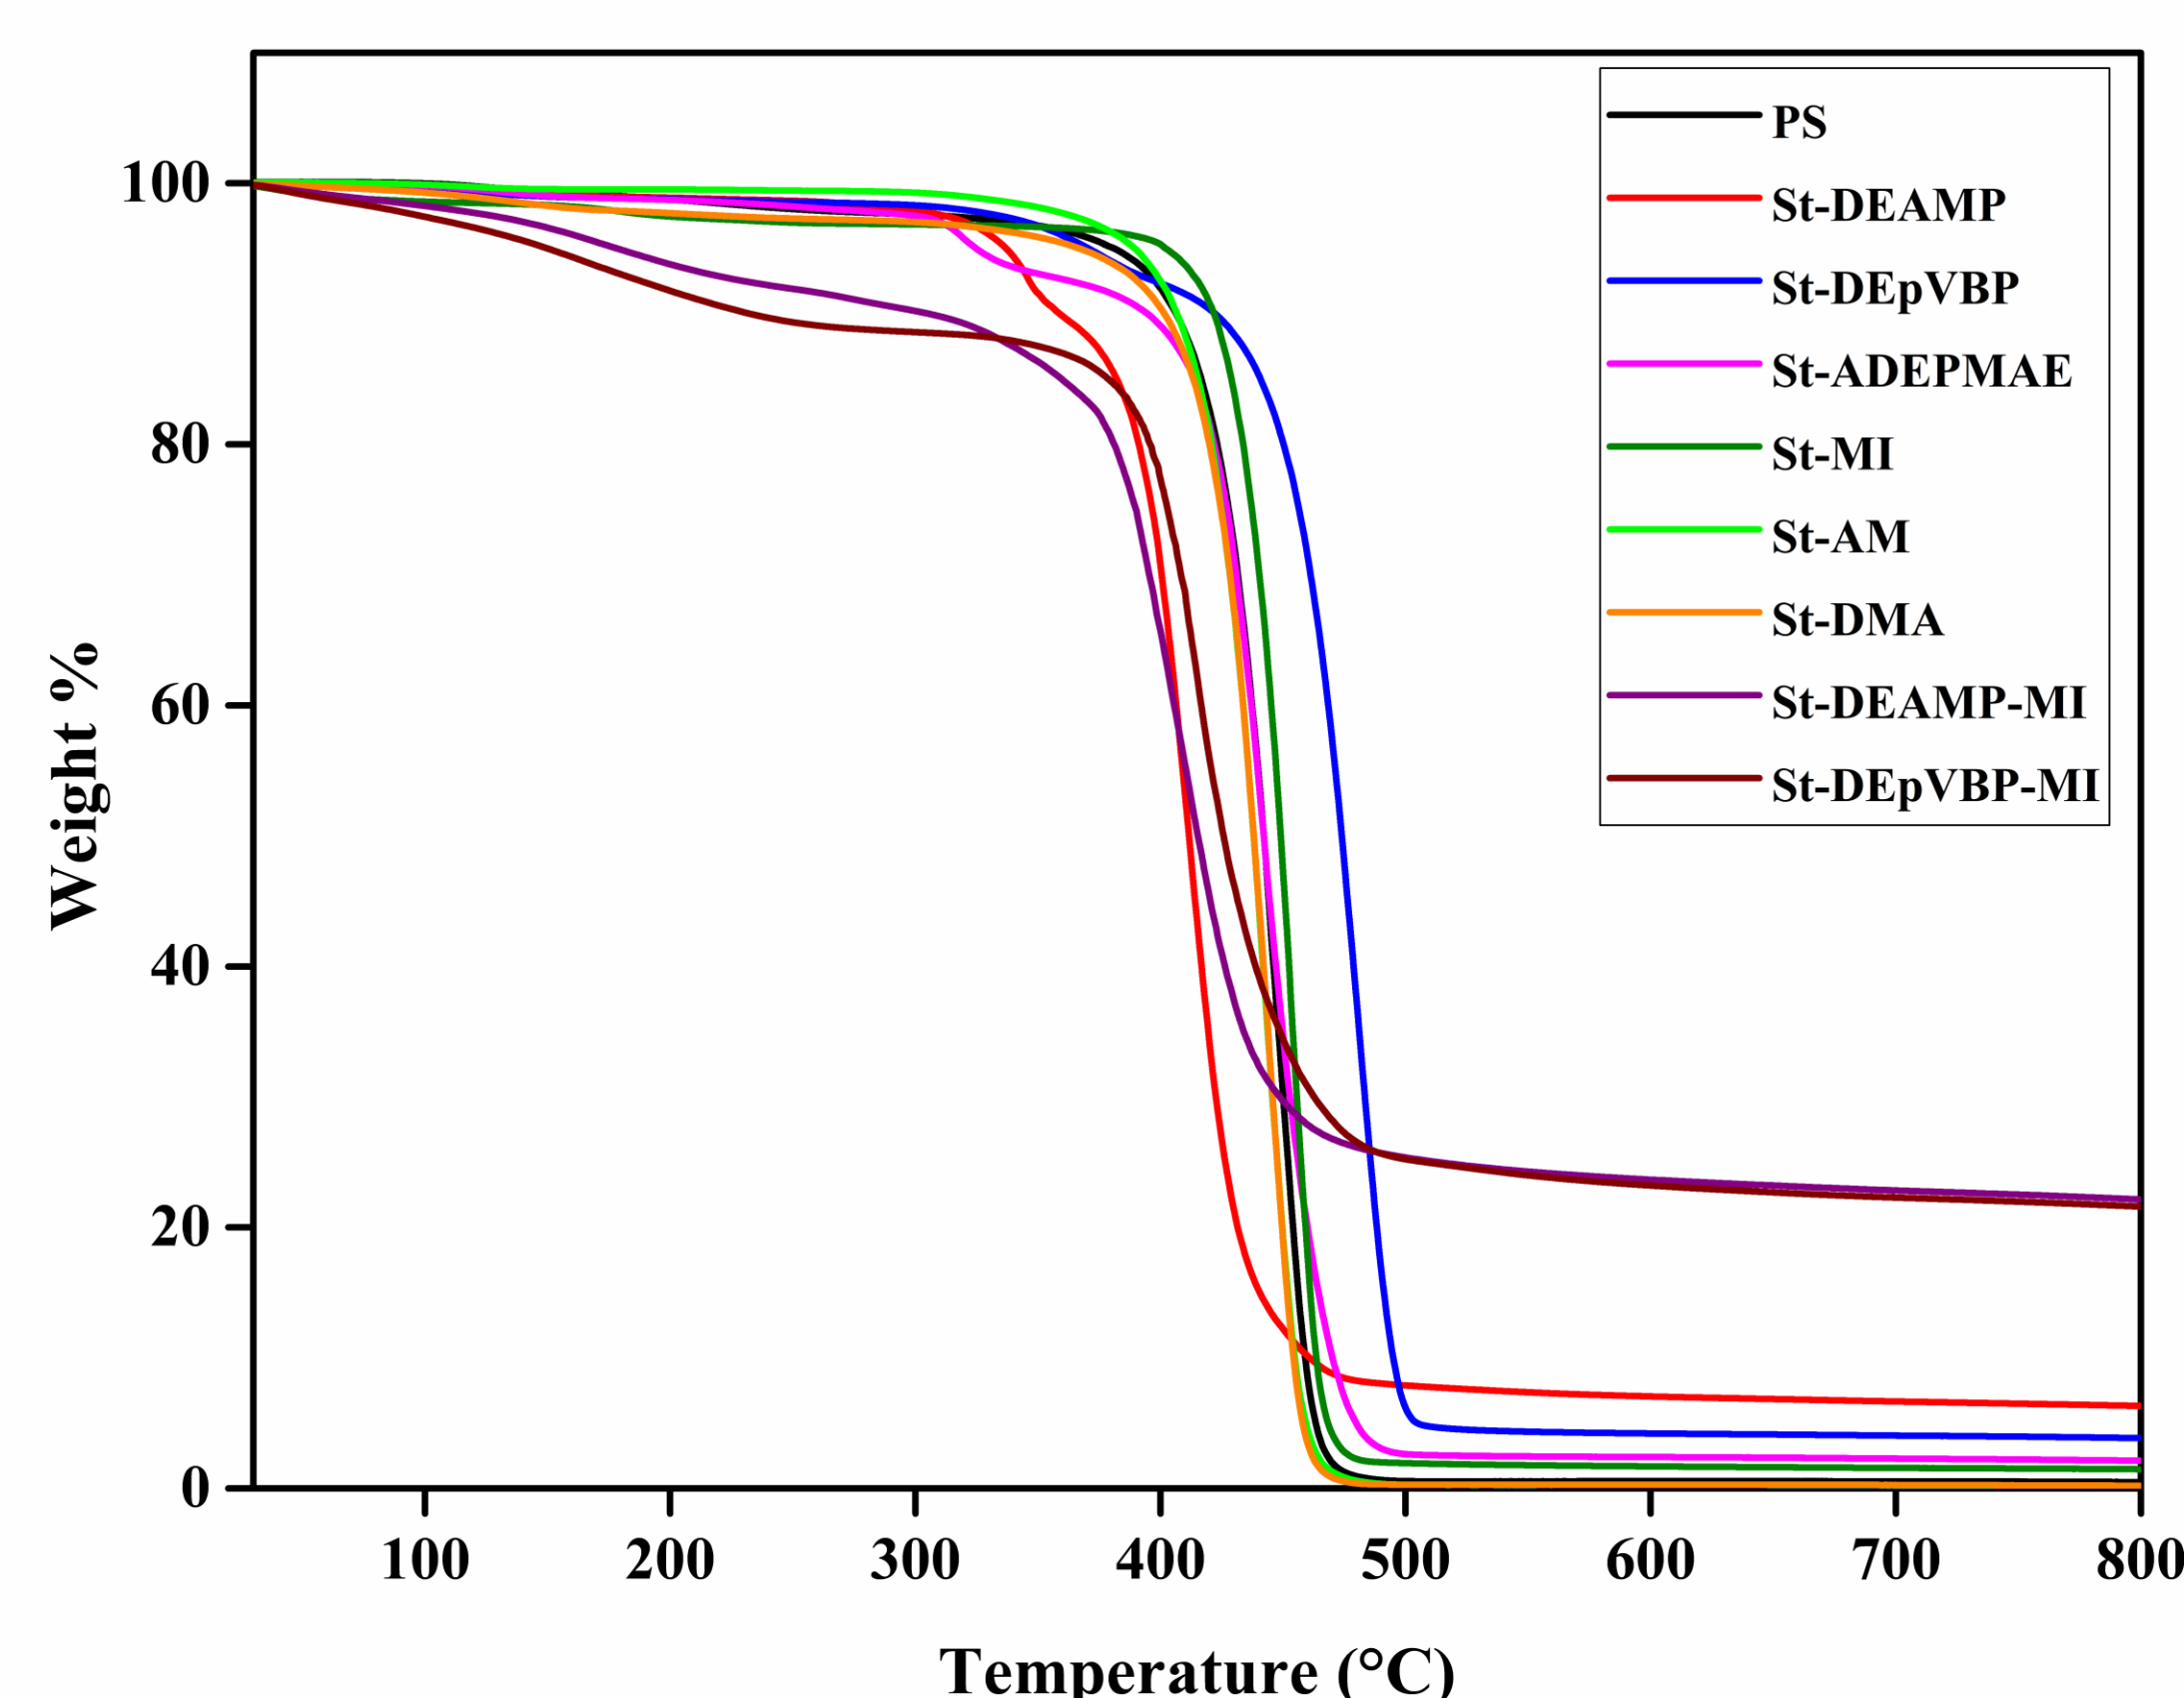


Figure 2: TG curves obtained at 10 °C/min for styrenic polymers in nitrogen atmosphere

## Conclusions

- The reactive modification of PS with P-, P/N- and N- containing monomers is found to be effective on improving the fire retardancy of PS.
- The general degradation profiles of co- and *ter*-polymers were found to be different from that of the unmodified PS, particularly, in terms of the degradation temperature, slopes and the amounts of char residues produced.
- Among various co-polymers, St-DEAMP, St-DEpVBP and St-MI exhibited better fire retarding performance compared to PS.
- The significant improvement observed for *ter*-polymers proved that P-N synergism can enhance the fire retardance of PS.
- As it is known that P-N synergism promotes charring during the combustion process, it is more pronounced in *ter*-polymers containing different P- and N- groups (an increase of nearly 90%), than that of polymer (St-ADEPMAE) containing direct P-N bond.
- The exact fire retarding mechanism of these *ter*-polymers is not proposed at present, which is under study.

## References

- Morgan A.B.: The Future of Flame Retardant Polymers-Unmet Needs and Likely New Approaches. *Polymer Reviews*, **59**, 25–54 (2018).
- Joseph P., Tretsiakova-McNally S.: Reactive Modifications of Some Chain- and Step-Growth Polymers with Phosphorus-Containing Compounds: Effects on Flame Retardance-A Review. *Polymers for Advanced Technologies*, **22**, 395-406. (2011).